

Environmental Certification Scheme

Carpet Name: **CROSSING IN TIME**


Licensee: **VICTORIA CARPETS**
Licence Number: **1005**
Label Number: **18049**

Certification Approved: **25/07/2018**

Level: **3**

ACCS Contract Grading: **CEHD 4***
ACCS Residential Grading: **REHD2 6***
Suitable for Stairs: **Yes**

Date Printed: **25/07/2018**

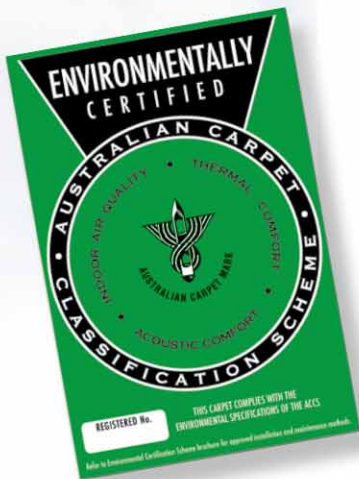

Allan Firth



Allan Firth
Secretary ACCS



Administered by the Carpet Institute of Australia Limited ABN 11 006 829 303
PO Box 7172, St Kilda Road, Melbourne Victoria 8004 Tel: (03) 9804 5559 • Fax: (03) 9804 5560
Email: info@carpetoz.com.au • www.carpetinstitute.com.au

This certificate remains the property of the Carpet Institute of Australia Limited.

Carpet Details:

Company: VICTORIA CARPETS

Label No: 18049

Licence No: 1005

Office No: 6655

Names:

CROSSING IN TIME

Details:

Awarded Res Grade: REHD2 6*
 Awarded Con Grade: CEHD 4*
 Registered On: 25/05/2018
 Active: Yes
 Date In-Active:
 Manufacture Method: Tufted
 Twist Set: N/A
 Dyeing Method: Melt Dyed
 #Colours/Designs: 7
 Backing Type: Other
 Felted: N/A
 Spinning System: BCF
 Insect Resist Agent: N/A
 Filament: 22
 Master Product:

Test Results:

Pile Mass g/m² (oz/yd²): 881 (26.0)
 SPM g/m² (oz/yd²): 394 (11.6)
 Stated Pile Height (mm): 5.2
 Minimum Pile Height (mm): 4.0
 Maximum Pile Height (mm): 5.5
 Dynamic Loading Loss (%): 0.0
 Static Loading Loss (%): 0.0
 Tex (g/1000m): 268
 Measured Pile Thickness (mm): 3.1
 Machine Gauge (Tufts/dm): 39.4
 Meas Tufts Perp to Selvedge: 39.5
 Meas Tufts Para to Selvedge: 48.3
 Treated For Soiling Resistance: Yes
 Soil Resist Inhibitor: Yes
 Stain Resist Inhibitor: Yes

Hexapod Scores:

	Texture		Colour		Thickness	
	WA	WA	WA	WA	(mm)	(%)
1500:	4.5	4.5	4.5	4.5	0.4	11.6
8000:	3.5	3.0	4.0	4.0	0.9	29.4

Quality Assurance Test:

Cut Pile (%): 0
 Loop Pile (%): 100
 Panel Assessment Contract: 15
 Panel Assessment Residential: 15
 Suitable For Stairs: Yes
 Tile: Yes SheetGoods: No
 Fibre Signature: NBA:100

ACCS Test:

	Con	Res	Max
SPM/PH Ratio:	13.5	16	16
Volume Density:	13.6	13.6	20
Tuft Density:	9	9	9
Dyn Load:	3.9	3.9	5
Stat Load:	4.1	4.1	5
Soiling Prop:	14	14	16
Abrasion Res:	10	10	10
Sub Total:	68.1	70.6	81
Panel Assess:	15	15	19
Total:	83.1	85.6	100
Calc Residential Grade:	REHD2	6*	
Calc Contract Grade:	CHD	3*	

Calculations

Pile Height(mm): 3.9
 Tuft Density(per dm²): 1907.8
 GSPM(g/m²): 415.0
 GSPM (abrasive) (g/m²): 275.0
 Soiling Propensity: 12.0 +2.0

OAF Values

OAF: 4.2
 Calc Density (+-5%): 0.12 0.127 0.13
 Base Fibre: NYLON
 Benchmarks:
 RHD1 0 RHD2 3.5
 REHD1 3.5 REHD2 3.5

Environmental Classification:

ECS: Yes
 Level: 3

	Calc	B/M	P/F
Acoustic:	3.1	3	PASS
Thermal:	24.4	15	PASS
VOC:			
TVOC	128		

Notes:

25/5/18 Submitted by R Canovan. 30/5/18 Panel graded REHD(S) 6* and CEHD(S) 4*.
 25/6/18 Submitted for ECS 3 by R Canovan. 27/6/18 Needs Acoustic report. 20/7/18
 New AWTA retest report shows Pile Thickness=3.1mm. Data entered. 25/7/18 Panel certified to ECS Level 3.